

# **VDM® Alloy 22**

## **Nicrofer 5621 hMoW**

# VDM® Alloy 22

## Nicrofer 5621 hMoW

VDM® Alloy 22 is a nickel-chromium-molybdenum alloy with tungsten and extremely low carbon and silicon content.

VDM® Alloy 22 is characterized by:

- Extraordinary resistance across a wide range of corrosive media under oxidizing and reducing conditions
- Particularly high resistance to crevice, pitting, and stress corrosion

### Designations

| Standard | Material designation |
|----------|----------------------|
| EN       | 2.4602 – NiCr21Mo14W |
| ISO      | NiCr21Mo14W3         |
| UNS      | N06022               |

### Standards

| Product form | ASTM  | ASME   | DIN   | ISO   | NACE              | sonstige         |
|--------------|-------|--------|-------|-------|-------------------|------------------|
| Sheet, plate | B 575 | SB 575 | 17750 | 6208  | MR 0103/ISO 17945 | VdTÜV 479        |
|              |       |        | 17744 | 9722  | MR 0175/ISO 15156 |                  |
| Strip        | B 575 | SB 575 | 17744 | 18274 | MR 0175/ISO 15156 |                  |
|              |       |        |       | 6208  |                   |                  |
| Rod, bar     | B 574 | SB 574 | 17744 |       | MR 0175/ISO 15156 | VdTÜV 479        |
|              | B 564 | SB 564 | 17752 |       | MR 0103/ISO 17945 |                  |
| Wire         |       |        | 17744 |       |                   | DIN EN ISO 18274 |

Table 1 – Designations and standards

# Chemical composition

|      | Cr   | Mo   | Ni   | Fe  | W   | Co  | Mn   | V    | Si   | P     | C     | S    |
|------|------|------|------|-----|-----|-----|------|------|------|-------|-------|------|
| Min. | 20.0 | 12.5 |      | 2.0 | 2.5 |     |      |      |      |       |       |      |
| Max. | 22.5 | 14.5 | bal. | 6.0 | 3.5 | 2.5 | 0.50 | 0.35 | 0.08 | 0.025 | 0.015 | 0.02 |

Due to technical reasons the alloy may contain additional elements

Table 2 – Chemical composition (%) according to ASTM B575

# Physical properties

| Density  | Melting range                        | Brinell Hardness |
|--|--------------------------------------|------------------|
| 8.7 g/m <sup>3</sup> at 20 °C<br>543 lb/ft <sup>3</sup> at 68 °F | 1,360 – 1,400 °C<br>2,470 – 2,550 °F | 240              |

| Temperature |       | Specific heat capacity |                | Thermal conductivity |                             | Electrical resistivity | Modulus of elasticity |                     | Coefficient of thermal expansion 20 °C (68 °F) to T |                        |
|-------------|-------|------------------------|----------------|----------------------|-----------------------------|------------------------|-----------------------|---------------------|---|------------------------|
| °C          | °F    | J<br>kg · K            | Btu<br>lb · °F | W<br>m · K           | Btu · in<br>sq. ft · h · °F | μΩ · cm                | GPa                   | 10 <sup>3</sup> ksi | 10 <sup>-6</sup><br>K                               | 10 <sup>-6</sup><br>°F |
| 0           | 32    | 402                    | 0.096          |                      |                             |                        | 207                   | 30                  |   |                        |
| 20          | 68    | 406                    | 0.097          | 9.4                  | 65.2                        | 121                    | 206                   | 29.9                |   |                        |
| 100         | 212   | 423                    | 0.101          | 11.1                 | 77.0                        | 123                    | 202                   | 29.3                | 12.4  | 6.89                   |
| 200         | 392   | 444                    | 0.106          | 13.4                 | 92.9                        | 123                    | 197                   | 28.6                | 12.4  | 6.89                   |
| 300         | 572   | 460                    | 0.11           | 15.5                 | 107                         | 125                    | 190                   | 27.6                | 12.5  | 6.94                   |
| 400         | 752   | 476                    | 0.114          | 17.5                 | 121                         | 126                    | 185                   | 26.8                | 13.1  | 7.28                   |
| 500         | 932   | 495                    | 0.118          | 19.5                 | 135                         | 127                    | 178                   | 25.8                | 13.7  | 7.61                   |
| 600         | 1,112 | 514                    | 0.123          | 21.3                 | 148                         | 128                    | 173                   | 25.1                | 14.3  | 7.94                   |
| 700         | 1,292 | 533                    | 0.127          | 23.2                 | 161                         | 129                    | 167                   | 24.2                | 14.9  | 8.28                   |
| 800         | 1,472 |                        |                |                      |                             |                        | 159                   | 23.1                | 15.5  | 8.61                   |
| 900         | 1,652 |                        |                |                      |                             |                        | 150                   | 21.8                | 15.8  | 8.78                   |
| 1,000       | 1,832 |                        |                |                      |                             |                        | 143                   | 20.7                | 16.2  | 9.0                    |

Table 3 – Typical physical properties at room and elevated temperatures

# Microstructural properties

VDM® Alloy 22 has a cubic, face-centered crystal structure.

# Mechanical properties

The following minimum values at room and increased temperatures apply to the solution-annealed condition for longitudinal and traverse test samples of the specified dimensions. The properties for larger dimensions must be agreed upon separately.

| Temperature |     | Yield strength<br>R <sub>p 0.2</sub> |      | Yield strength<br>R <sub>p 1.0</sub> |      | Tensile strength<br>R <sub>m</sub> |         | Elongation<br>A |
|-------------|-----|--------------------------------------|------|--------------------------------------|------|------------------------------------|---------|-----------------|
| °C          | °F  | MPa                                  | ksi  | MPa                                  | ksi  | MPa                                | ksi     | %               |
| 20          | 68  | 310                                  | 45   | 335                                  | 48.6 | 690-950                            | 100-138 | 45              |
| 100         | 212 | 270                                  | 39.2 | 290                                  | 42.1 |                                    |         |                 |
| 200         | 392 | 225                                  | 32.6 | 245                                  | 35.5 |                                    |         |                 |
| 300         | 300 | 195                                  | 28.3 | 215                                  | 31.2 |                                    |         |                 |
| 400         | 752 | 175                                  | 25.4 | 195                                  | 28.3 |                                    |         |                 |

Table 4 – Mechanical properties at room and elevated temperatures. Minimum values according to VdTÜV Sheet 479

| Product form | Dimension |            | Yield strength<br>R <sub>p 0.2</sub> |     | Yield strength<br>R <sub>p 1.0</sub> |      | Tensile strength<br>R <sub>m</sub> |     | Elongation<br>A |
|--------------|-----------|------------|--------------------------------------|-----|--------------------------------------|------|------------------------------------|-----|-----------------|
|              | mm        | in         | MPa                                  | ksi | MPa                                  | ksi  | MPa                                | ksi | %               |
| Plate        | ≤ 3       | 0.118      | ≥ 310                                | 45  | ≥ 335                                | 48.6 | ≥ 690                              | 100 | ≥ 45            |
| Coil         | ≤ 3       | 0.118      | ≥ 310                                | 45  | ≥ 335                                | 48.6 | ≥ 690                              | 100 | ≥ 45            |
| Plate        | 3-50      | 0.118-1.97 | ≥ 310                                | 45  | ≥ 335                                | 48.6 | ≥ 690                              | 100 | ≥ 45            |
| Bar          | 10-90     | 0.394-3.54 | ≥ 310                                | 45  | ≥ 335                                | 48.6 | ≥ 690                              | 100 | ≥ 45            |

Table 5 – Mechanical properties at room temperature. Minimum values according to VdTÜV Sheet 479

## ISO V-notch impact energy KV<sub>2</sub>

| Minimum value       | Minimum value      |
|---------------------|--------------------|
| 20 °C (68 °F)       | -196 °C (-321 °F)  |
| 120 J (88.5 ft-lbs) | 96 J (22.9 ft-lbs) |

1) Average value of 3 samples. Only one value may fall below the minimum average value, and by no more than 30%. The values also apply for the heat affected zones in welded joints.

2) These values only apply for normal samples according to DIN EN ISO 148-1. For undersized samples according to DIN EN ISO 148-1, the minimum values indicated for the notch impact toughness must be reduced in a manner that is linear to the sample cross-section in the gap. For undersized samples <5mm according to DIN EN ISO 148-1, the values for the individual case must be coordinated with the manufacturer separately.

# Corrosion resistance

Due to the extremely low carbon and silicon concentrations, VDM® Alloy 22 has no propensity for grain boundary dispersions in hot forming or welding. This alloy can therefore be used in many chemical processes with both oxidizing and reducing media when welded. The high chrome, molybdenum, and nickel concentrations make the alloy resistant to chloride ion attacks. The tungsten concentration further increases this resistance. VDM® Alloy 22 is resistant to chlorine gas, hypochlorite, and chlorine dioxide solutions such as those that can be encountered in the cellulose industry. The alloy is characterized by excellent resistance to concentrated solutions of oxidizing salts (such as iron III and copper chloride).

# Applications

VDM® Alloy 22 has a broad field of application in the chemicals and petrochemicals industry and is used for components in organic processes that contain chloride and for catalytic systems. The material is especially effective in hot, contaminated mineral acids, solutions, organic acids (such as formic acid and acetic acid) or sea water.

Other fields of application are:

- Acetic acid production
- Pharmaceuticals industry
- Fine chemicals

# Fabrication and heat treatment

VDM® Alloy 22 can be easily formed both hot and cold and can also be machined

## Heating

It is important that the workpieces are clean and free of any contaminations before and during heat treatment. Sulfur, phosphorus, lead and other low-melting point metals can result in material damage during the heat treatment. This type of contamination is also contained in marking and temperature-indicating paints or pens, and also in lubricating grease, oils, fuels and similar materials. The sulfur content of fuels must be as low as possible. Natural gas should contain less than 0.1 wt.-% of sulfur. Heating oil with a maximum sulfur content of 0.5 wt.-% is also suitable. Electric furnaces are preferable for their precise temperature control and a lack of contaminations from fuels. The furnace temperature should be set between neutral and slightly oxidizing and it should not change between oxidizing and reducing. The workpieces must not come into direct contact with flames.

## Hot forming

The material can be hot-formed in a temperature range between 1,100 and 900 °C (2,012 °F-1,652 °F) with subsequent rapid cooling down in water or air. Heat treatment after hot forming is recommended in order to achieve optimal properties. For heating up, workpieces should be placed in a furnace that is already heated up to the target value.

## Cold forming

VDM® Alloy 22 has higher work hardening rate than other austenitic stainless steels. This should be taken into account when selecting forming equipment. The workpiece should be in the solution-annealed condition. Intermediate annealing is necessary for major cold forming work. For cold forming above 15%, new solution annealing must be conducted.

## Heat treatment

Solution annealing should take place at temperatures between 1,105 and 1,135 °C (2,021-2,075 °F).

Cooling down should be accelerated with water to achieve optimum corrosion properties. Fast air cooling can also be carried out at thicknesses of less than approx. 1.5 mm. For strip and wire products, the heat treatment can be performed in a continuous furnace at a speed and temperature that is adapted to the material thickness. In each heat treatment, the aforementioned cleanliness requirements must be observed.

## Descaling and pickling

Oxides of VDM® Alloy 22 and heat tint in the area around welds adhere more strongly than in stainless steels. Grinding using extremely fine abrasive belts or grinding discs is recommended. It is imperative that grinding burns be avoided. Before pickling in nitric-hydrofluoric acid, the oxide layers should be destroyed by abrasive blasting or fine grinding, or pre-treated in salt baths. The pickling baths used should be carefully monitored with regard to concentration and temperature.

## Machining

VDM® Alloy 22 should be machined in the solution-annealed condition. Because of the considerably elevated tendency toward work hardening in comparison with low-alloy austenitic stainless steels, a low cutting speed and a feed level that is not too high should be selected and the cutting tool should be engaged at all times. An adequate chip depth is important in order to cut below the previously formed strain-hardened zone. An optimal heat dissipation by using large quantities of suitable, preferably aqueous, cold forming lubricants has considerable influence on a stable machining process.

# Welding information

When welding nickel alloys and special stainless steels, the following information should be taken into account:

## **Safety**

The generally applicable safety recommendations, especially for avoiding dust and smoke exposure must be observed.

## **Workplace**

A separately located workplace, which is specifically separated from areas in which C-steel is being processed, must be provided. Maximum cleanliness is required, and drafts should be avoided during gas-shielded welding.

## **Auxiliary equipment and clothing**

Clean fine leather gloves and clean working clothes must be used.

## **Tools and machines**

Tools that have been used for other materials may not be used for nickel alloys and stainless steels. Only stainless steel brushes may be used. Processing and treatment machines such as shears, punches or rollers must be fitted (felt, cardboard, films) so that the workpiece surfaces cannot be damaged by the pressing in of iron particles through such equipment, as this can lead to corrosion.

## **Edge preparation**

Welding seam preparation should preferably be carried out using mechanical methods through lathing, milling or planing. Abrasive waterjet cutting or plasma cutting is also possible. In the latter case, however, the cut edge (seam flank) must be cleanly reworked. Careful grinding without overheating is also permissible.

## **Striking the arc**

The arc should only be struck in the seam area, such as on the weld edges or on an outlet piece, and not on the component surface. Scaling areas are areas in which corrosion more easily occurs.

## **Included angle**

Compared to C-steels, nickel alloys and special stainless steels exhibit lower heat conductivity and greater heat expansion. These properties must be taken into account by larger root openings or root gaps (1 to 3 mm, 0.039 to 0.118 in). Due to the viscosity of the welding material (compared to standard austenites) and the tendency to shrink, opening angles of 60 to 70° – as shown in Figure 1 – have to be provided for butt welds.

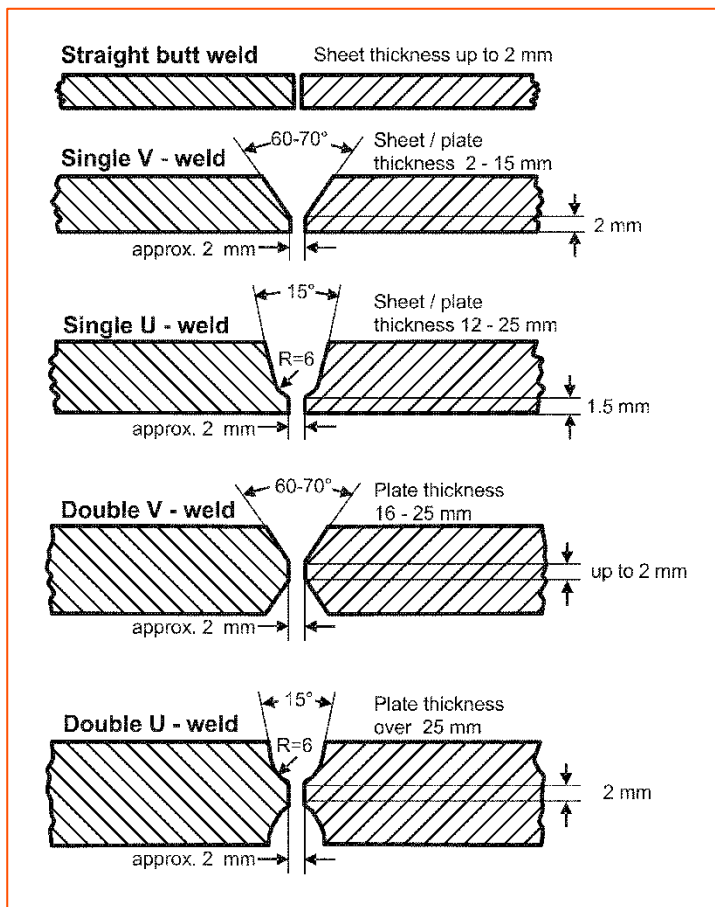


Figure 1 – Seam preparation for welding nickel alloys and special stainless steels

### Cleaning

Cleaning of the base material in the seam area (both sides) and the welding filler (e.g. welding rod) should be carried out using acetone.

### Welding parameters and influence

It must be ensured in the welding process that work is carried out using targeted heat application, low heat input and rapid heat extraction. The interpass temperature should not exceed 120°C (248 °F). In principle, welding parameters must be checked.

### Welding filler

VDM® Alloy 22 can be welded using all conventional processes.

The following welding filler is recommended:

VDM® FM 622 (mat. no. 2.4635)  
 ISO 18274 - S Ni 6022 (NiCr21Mo13Fe4W3)  
 AWS 5.14 - ERNiCrMo10

VDM® FM 59 (mat. no. 2.4607)  
 ISO 18274 - S Ni 6059 (NiCr23Mo16)  
 AWS 5.14 - ERNiCrMo-13



To achieve optimum corrosion properties, the TIG method is preferable.

**Weld strip**

VDM® WS 59 (material no. 2.4607)

ISO 18274 - B Ni 6059 (NiCr23Mo16)

AWS 5.14 - ERNiCrMo-13

**Bar electrodes in sleeves**

The use of bar electrodes in sleeves is possible.

**Post-treatment**

If the work is performed optimally, brushing immediately after welding, i.e. while still warm and without additional pickling, will result in the desired surface condition. In other words, heat tints can be removed completely. Pickling, if required or specified, should generally be the last work step in the welding process. The information contained in the section entitled "Descaling and pickling" must be observed. Heat treatments are normally neither required before nor after welding.

| Thickness<br>Mm<br>(in) | Welding<br>technique  | Filler material               |                  | Root pass <sup>1)</sup> |          | Intermediate<br>and final passes |          | Welding<br>speed<br>(cm/min) | Shielding gas             |                 |
|-------------------------|-----------------------|-------------------------------|------------------|-------------------------|----------|----------------------------------|----------|------------------------------|---------------------------|-----------------|
|                         |                       | Diameter<br>mm<br>(in)        | Speed<br>(m/min) | I in (A)                | U in (V) | I in (A)                         | U in (V) |                              | Type                      | Rate<br>(l/min) |
| 3<br>(0.118)            | m-WIG                 | 2.0<br>(0.079)                |                  | 90                      | 10       | 110-120                          | 11       | 15                           | I1, R1 with<br>max. 3% H2 | 8-10            |
| 6<br>(0.236)            | m-WIG                 | 2.0-2.4<br>(0.079-<br>0.0945) |                  | 100-110                 | 10       | 120-140                          | 12       | 14-16                        | I1, R1 with<br>max. 3% H2 | 8-10            |
| 8<br>(0.315)            | m-WIG                 | 2.4<br>(0.045)                |                  | 100-110                 | 11       | 130-140                          | 12       | 14-16                        | I1, R1 with<br>max. 3% H2 | 8-10            |
| 10<br>(0.394)           | m-WIG                 | 2.4<br>(0.0945)               |                  | 100-110                 | 11       | 130-140                          | 12       | 14-16                        | I1, R1 with<br>max. 3% H2 | 8-10            |
| 3<br>(0.118)            | v-WIG <sup>2)</sup>   | 1.0-1.2<br>(0.039-<br>0.0472) | 1.2              |                         |          | 150                              | 11       | 25                           | I1, R1 with<br>max. 3% H2 | 12-14           |
| 5<br>(0.197)            | v-WIG <sup>2)</sup>   | 1.2<br>(0.0472)               | 1.4              |                         |          | 180                              | 12       | 25                           | I1, R1 with<br>max. 3% H2 | 12-14           |
| 2<br>(0.0787)           | v-WIG HD              | 1.0<br>(0.039)                |                  |                         |          | 180                              | 11       | 80                           | I1, R1 with<br>max. 3% H2 | 12-14           |
| 10<br>(0.394)           | v-WIG HD              | 1.2<br>(0.0472)               |                  |                         |          | 220                              | 12       | 40                           | I1, R1 with<br>max. 3% H2 | 12-14           |
| 4<br>(0.157)            | Plasma <sup>3)</sup>  | 1.2<br>(0.0472)               | 1.0              | 180                     | 25       |                                  |          | 30                           | I1, R1 with<br>max. 3% H2 | 30              |
| 6<br>(0.236)            | Plasma <sup>3)</sup>  | 1.2<br>(0.0472)               | 1.0              | 200-220                 | 26       |                                  |          | 26                           | I1, R1 with<br>max. 3% H2 | 30              |
| 8<br>(0.315)            | MIG/MAG <sup>4)</sup> | 1.0<br>(0.039)                | 6-7              |                         |          | 130-140                          | 23-27    | 24-30                        | I1                        | 18              |
| 10<br>(0.394)           | MIG/MAG <sup>4)</sup> | 1.2<br>(0.0472)               | 6-7              |                         |          | 130-150                          | 23-27    | 25-30                        | I1                        | 18              |

#### Information

<sup>1)</sup> Root pass: it must be ensured that there is sufficient root protection, for example using Ar 4.6, for all inert gas welding processes.

<sup>2)</sup> Autom. TIG: the root pass should be welded manually (see manual TIG parameters)

<sup>3)</sup> Plasma: recommended plasma gas Ar 4.6 / plasma quantity 3.0-3.5 l/min

<sup>4)</sup> GMAW (MIG/MAG): the use of multi-component shielding gases is recommended for MAG welding.

Section energy kJ/cm: autom. TIG-HD max. 6; TIG, GMAW (MIG/MAG) manual, mechanized max. 8; plasma max. 10

The values are intended as guidance to simplify the setting of welding machines.

Table 6 – Welding parameters

# Availability

VDM® Alloy 22 is available in the following standard semi-finished forms:

## Sheet

Delivery condition: Hot or cold rolled, heat treated, descaled or pickled

| Condition   | Thickness<br>mm (in) | Width<br>mm (in)         | Length<br>mm (in) | Piece weight<br>Kg (lb) |
|-------------|----------------------|--------------------------|-------------------|-------------------------|
| Cold rolled | 1-7 (0.039-0.275)    | 1000-2,500 (39.37-98.42) | ≤ 12,500 (492)    |                         |
| Hot rolled  | 3-70 (0.118-2.75)    | 1000-2,500 (39.37-98.42) | ≤ 12,500 (492)    | ≤ 3,600 (7,936.6)       |

## Strip

Delivery condition: Cold rolled, heat treated, pickled or bright annealed

| Thickness<br>mm (in)             | Width<br>mm (in)       | Coil-inside diameter<br>mm (in) |               |               |               |
|----------------------------------|------------------------|---------------------------------|---------------|---------------|---------------|
| 0,025-0,15<br>(0.000984-0.00591) | 4-230<br>(0.157-9.06)  | 300<br>(11.8)                   | 400<br>(15.7) | 500<br>(19.7) | –             |
| 0,15-0,25<br>(0.00591-0.00984)   | 4-720<br>(0.157-28.3)  | 300<br>(11.8)                   | 400<br>(15.7) | 500<br>(19.7) | –             |
| 0,25-0,6<br>(0.00984-0.0236)     | 6-750<br>(0.236-29.5)  | –                               | 400<br>(15.7) | 500<br>(19.7) | 600<br>(23.6) |
| 0,6-1<br>(0.0236 -0.0394)        | 8-750<br>(0.315-29.5)  | –                               | 400<br>(15.7) | 500<br>(19.7) | 600<br>(23.6) |
| 1-2<br>(0.0394-0.0787)           | 15-750<br>(0.591-29.5) | –                               | 400<br>(15.7) | 500<br>(19.7) | 600<br>(23.6) |
| 2-3<br>(0.0787-0.118)            | 25-750<br>(0.984-29.5) | –                               | 400<br>(15.7) | 500<br>(19.7) | 600<br>(23.6) |

Rolled sheet – separated from the coil – are available in lengths from 250-4,000 mm (9.84 to 157.48 in).

## Rod and bar

Delivery condition: Forged, rolled, drawn, heat treated, oxidized, descaled or pickled, turned, peeled, ground or polished

| Dimensions                   | Outside diameter<br>mm (in) | Length<br>mm (in)         |
|------------------------------|-----------------------------|---------------------------|
| General dimensions           | 6-800 (0.236-31.5)          | 1,500-12,000 (59.1 – 472) |
| Material specific dimensions | 10-600 (0.393-23.62)        | 1,500-12.000 (59.1 - 472) |

## Wire

Delivery condition: Drawn bright, ¼ hard to hard, bright annealed in rings, containers, on spools and headstocks

| Drawn<br>mm (in)     | Hot rolled<br>mm (in) |
|----------------------|-----------------------|
| 0.16-10 (0.006-0.04) | 5.5-19 (0.22-0.75)    |

Other shapes and dimensions such as discs, rings, seamless or longitudinally welded pipes and forgings can be requested.

# Publications

The following technical literature has been published about the material VDM® Alloy 22:

U. Heubner et al.: "Nickelwerkstoffe und hochlegierte Sonderedelstähle", expert Verlag, Renningen, 5th edition, 2012.

U. Heubner, M. Köhler: "Das Zeit - Temperatur - Ausscheidungs- und das Zeit - Temperatur - Sensibilisierungs - Verhalten von hochkorrosionsbeständigen Nickel - Chrom - Molybdän - Legierungen", Werkstoffe und Korrosion 43, 1992, pages 181-190.

# Legal notice

23.11.2020

**Publisher**

VDM Metals International GmbH  
Plettenberger Strasse 2  
58791 Werdohl  
Germany

**Disclaimer**

All information contained in this data sheet is based on the results of research and development work carried out by VDM Metals International GmbH and the data contained in the specifications and standards listed available at the time of printing. The information does not represent a guarantee of specific properties. VDM Metals reserves the right to change information without notice. All information contained in this data sheet is compiled to the best of our knowledge and is provided without liability. Deliveries and services are subject exclusively to the relevant contractual conditions and the General Terms and Conditions issued by VDM Metals. Use of the most up-to-date version of this data sheet is the responsibility of the customer.

VDM Metals International GmbH  
Plettenberger Strasse 2  
58791 Werdohl  
Germany

Phone +49 (0)2392 55 0  
Fax +49 (0)2392 55 22 17

[vdm@vdm-metals.com](mailto:vdm@vdm-metals.com)  
[www.vdm-metals.com](http://www.vdm-metals.com)